AD 645432

Rubber Research

The Synthesis of Special Fluorine-Containing Monomers

67-48-CM

Semi-Annual Report No. 2

U. S. Army Con      ¢ DA-19-129-AMC-869 N:

Project      (CO. 24401A329)

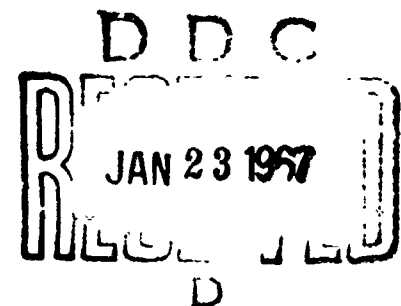For the Period June      1966 to December 1, 1966

December 15, 1966

by

J. D. Park and J. R. Lacher

Project Officer:  Dr. Malcolm Henry

University of Colorado

Boulder, Colorado

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of trade names in this report does not constitute an official indorsement or approval of the use of such items.

Destroy this report when no longer needed. Do not return it to the originator.

# ABSTRACT

Further work on the syntheses of fluorine containing olefins and diolefins is reported. Studies directed toward syntheses of derivatives of perfluoro-bicyclobutyl and perfluorobicyclobutenyl have been initiated. Of particular interest is the preparation of 2,2'-diiodo-per-fluorobicyclobutenyl by photolysis of 1,2-diiodotetrafluorocyclobutene.
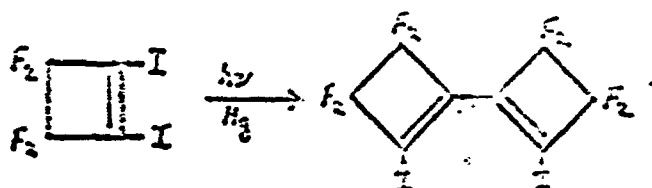


Starting from 1,2-dichlorohexafluorocyclopentene, other dihalo- and mixed dihalohexafluorocyclopentenes have been prepared, and from these have been prepared the monoethoxy derivatives, such as 1-iodo-2-ethoxyhexafluorocyclopentene.

# I.  INTRODUCTION

The purpose of this project is to carry out a basic chemistry research program for the purpose of synthesizing new potentially useful monomers containing fluorine. Monomers synthesized will consist of compounds both partially and completely fluorinated. In addition these fluorine containing monomers will have active sites of suitable activity for participation in homo-,co-, and terpolymerizations.

Olefinic and acetylenic fluorine compounds containing both conjugated or unconjugated unsaturation will be considered. In addition or as alternative sites of potential activity other organic functional groups may be substituted, as for example, carbonyl, nitroso, carboxylic or sulfone.

Methods of preparation of desired monomers may vary depending on the compound in question. Typical methods will include for example, dehydrohalogenations, dehalogenations, pyrolysis, decarboxylations, disproportionations and dimerizations.

This research is authorized under U. S. Army Contract DA-19-129-AMC-869(N) and is the second semi-annual report for the period June 1, 1966 to December 1, 1966 under this project with Dr. Malcolm Henry as project officer. Previously, similar researches authorized under Contract No. DA-129-1926(01 6028-62) under Dr. Malcolm Henry as project officer were summarized in three semi-annual reports and a final report and covered the period October 1, 1963 to October 1, 1965.

These reports should be used in conjunction with the present series to bring the historical portion up to date.

## II.  SUMMARY OF CURRENT PROGRESS

### Intermediate for Polymer Studies

The synthesis of a series of new olefins and diolefins are still in progress. These are possible candidates for polymer evaluation as well as basic intermediates for the synthesis of other monomers containing a hetero-atom or atoms. Some of the above types of compounds will be used to prepare highly sterically hindered nitroso monomers for evaluation as a possible candidate for polymerization.

The synthesis of 1,2-diiodo-3,3,4,4-tetrafluorocyclobutene has been developed and improved. Along similar lines, 1,2-diiodoperfluorocyclopentene has also been prepared. These two compounds will serve as valuable intermediates in the syntheses of dibasic acids, nitroso acids, dinitroso derivatives and possibly as sources for fluorinated keto-acids.
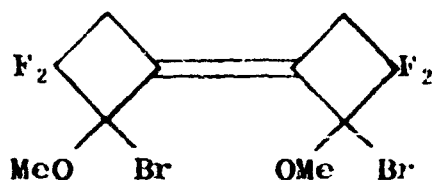
The following compounds have been synthesized and their properties obtained:
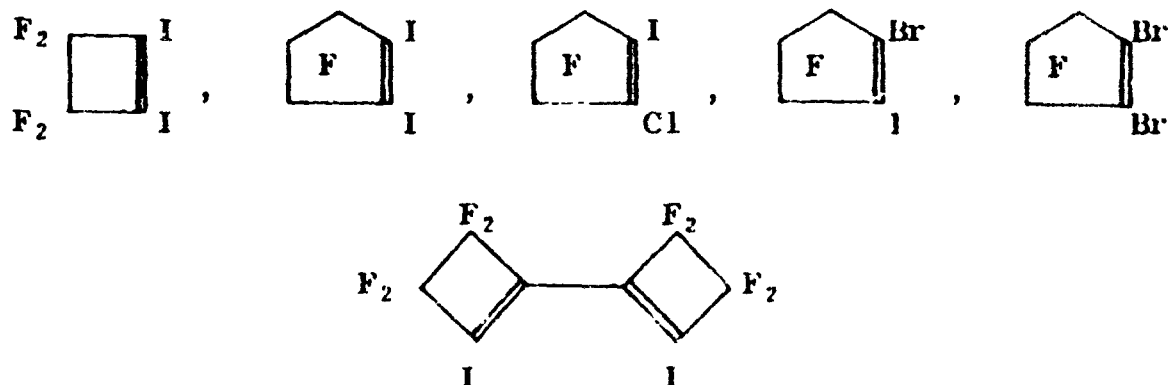


The following samples were prepared and sent to Dr. Douglas Relyea:

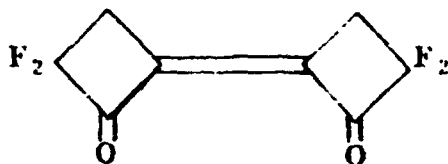FC-312                                                    18.2 g.
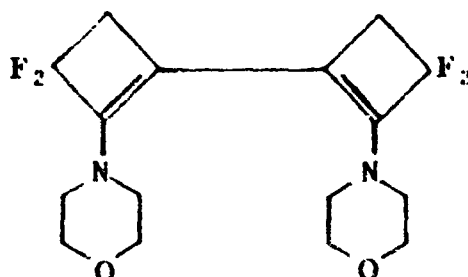


FC-313                                                    2.0 g.



FC-314                                                    22.0 g.

FC-315          2.0 g.

Polymer of

$$F_2 \underset{F_2}{\overline{\phantom{xx}}} \begin{array}{cc} C & C \\ C = C \end{array}$$
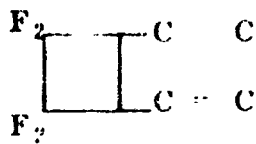
FC-316          5.0 g.

Disodium salt of

$$O= \Diamond \!\!-\!\! \Diamond \,\text{-} O$$
$$\phantom{O=}\text{OMe} \quad \text{OMe}$$

FC-317          7.0 g.

$$\left[\, F \,\right]^{I}_{Cl}$$

FC-318          7.0 g.

$$\left[\, F \,\right]^{I}_{I}$$
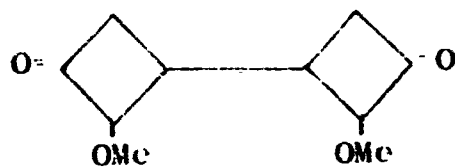
**TITLE:** Investigations on the Synthesis and Reactions of Perhalobicyclobuteneyl compounds.

### Part A: Synthesis Pathways

**OBJECT:** To develop a useful synthetic pathway to perhalobicyclobuteneyl compounds which should be important intermediates in the syntheses of diketodicarboxylic acids.

**HISTORICAL:** There are relatively few syntheses of bicyclobutyl or bicyclobuteneyl compounds (hereinafter referred to as dibox compounds) reported in the literature. An adequate review of earlier work in this area has been compiled by Frank.[1]

Prior to Frank's work, no general pattern for the synthesis of halogenated dibox compounds had been developed. Coffman, Barrick et al.[2] were the first to apply thermal cycloalkylation reactions to this end. They reacted butadiene with excess tetrafluoroethylene in a bomb under autogenous pressure to obtain a 10-15% yield of 2,2,2',2',3,3,3',3'-octafluorobicyclobutyl. In addition, they treated vinylacetylene with tetrafluoroethylene to give the products indicated below.
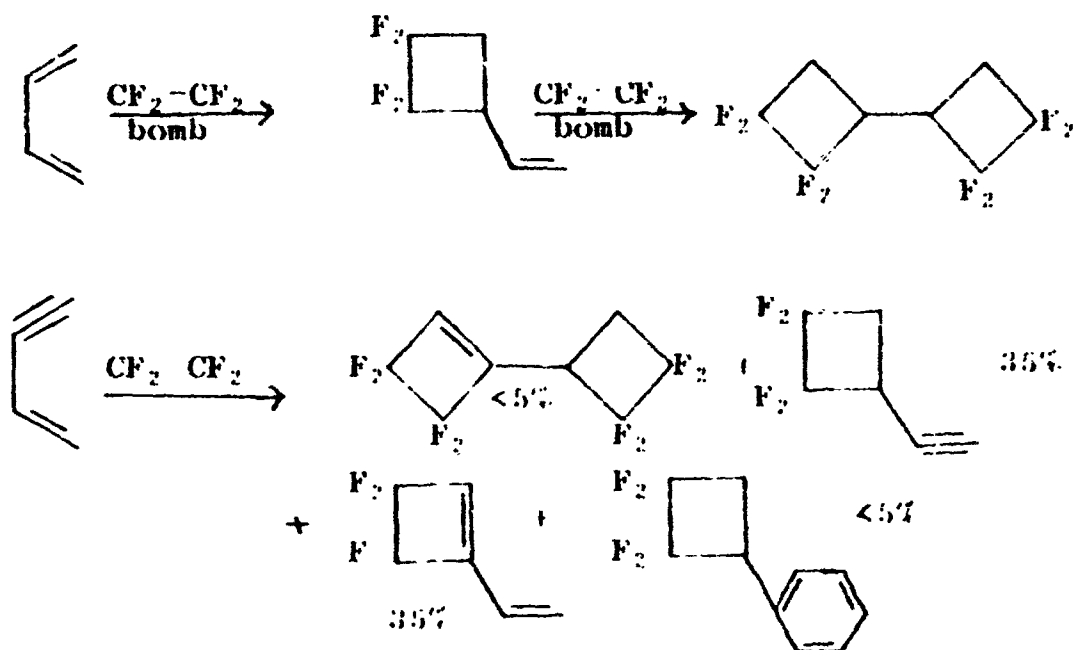


Shortly thereafter, Miller[3] accomplished a coupling of two perfluorobicyclobutene units in liquid fluorine at -78° to yield perfluorobicyclobutyl. The product was an inert liquid at 86-87°.
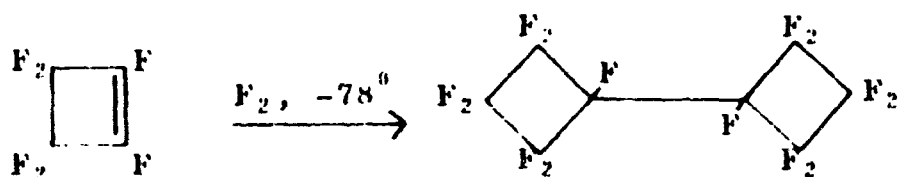
Pruett et al.[4] prepared a mixture of the dimer and trimer of perfluorocyclobutene by the treatment of the monomer with pyridine at $0°$.
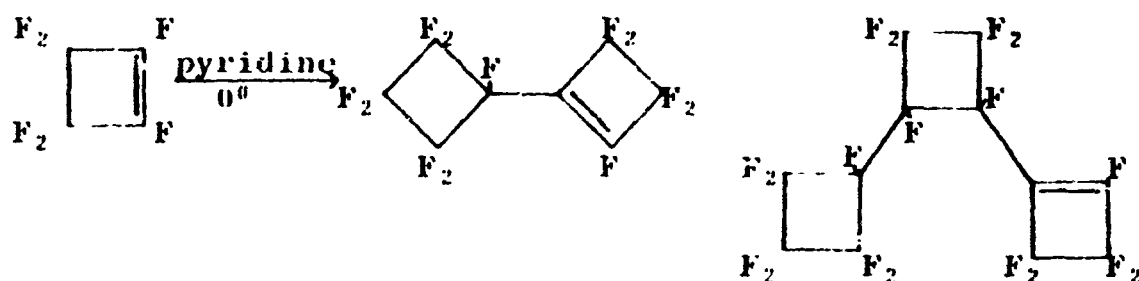
Sharts and Roberts[5] again applied thermal alkylation reactions in treating isopropenyl acetylene with chlorotrifluoroethylene to give the two expected 1:1 adducts and less than 5% of a dibox derivative. Similarly, Ryananova[6] et al. reported 10-15% yields of 2:1 adducts from the thermal addition of 1,3-butadiene to perfluorobutadiene.

R = -H, -CH₃
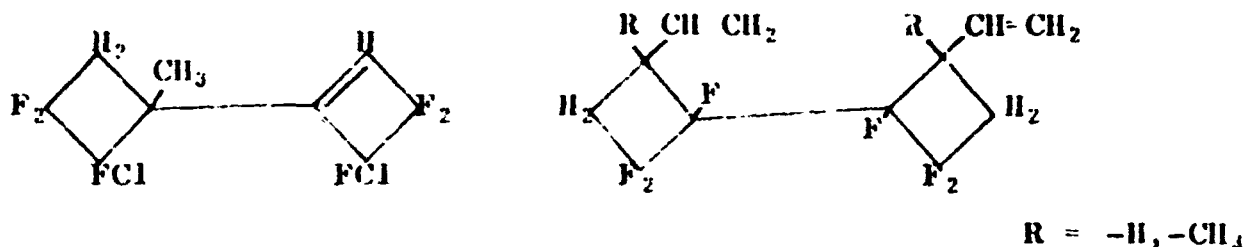
Frank of this laboratory extended the knowledge of thermal cycloalkylation reactions of haloethylenes in preparing cyclobutanes (several reviews have recently been published[2,7]) to the synthesis of dibox derivatives. In reacting 1,3-butadiene with trifluorochloroethylene in an autoclave he isolated 5-10% of a 1:2 adduct, 2,2'-dichloro-2,2',3,3,3',3'-hexafluoro-bicyclobutyl, in addition to the normal 1:1 adduct. Increasing the molar ratio of trifluorochloroethylene did not improve the yield of diadduct significantly.
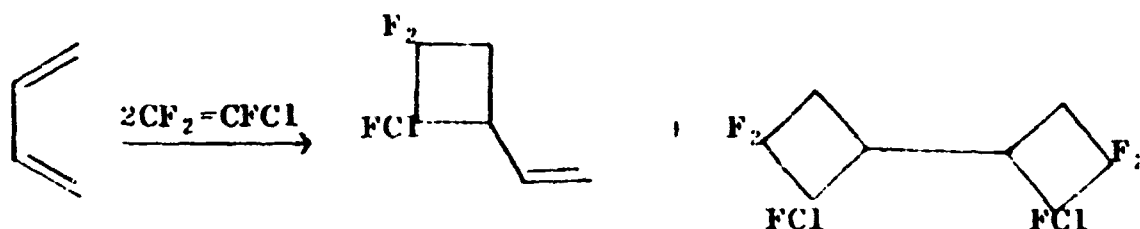
The following synthetic pathway ultimately proved most useful in the synthesis of dibox compounds.
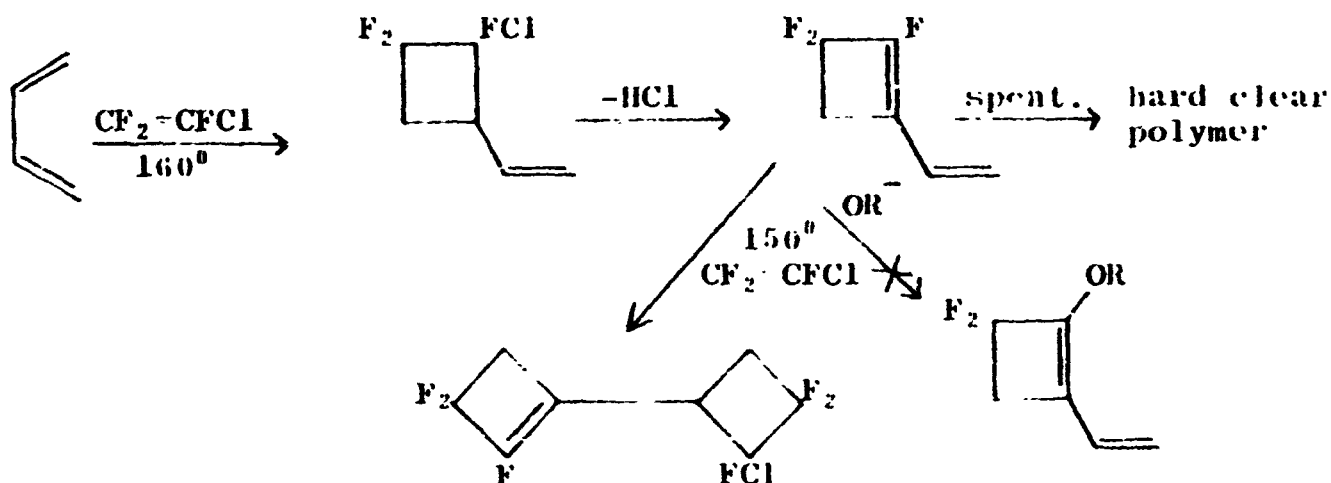
**RESULTS AND DISCUSSION:** It is apparent that a logical pathway to perhalobicyclobutenyl compounds would involve thermal addition of haloethylenes to 1,1,4,4-tetrafluorobutadiene followed by dehydrohalogenation.
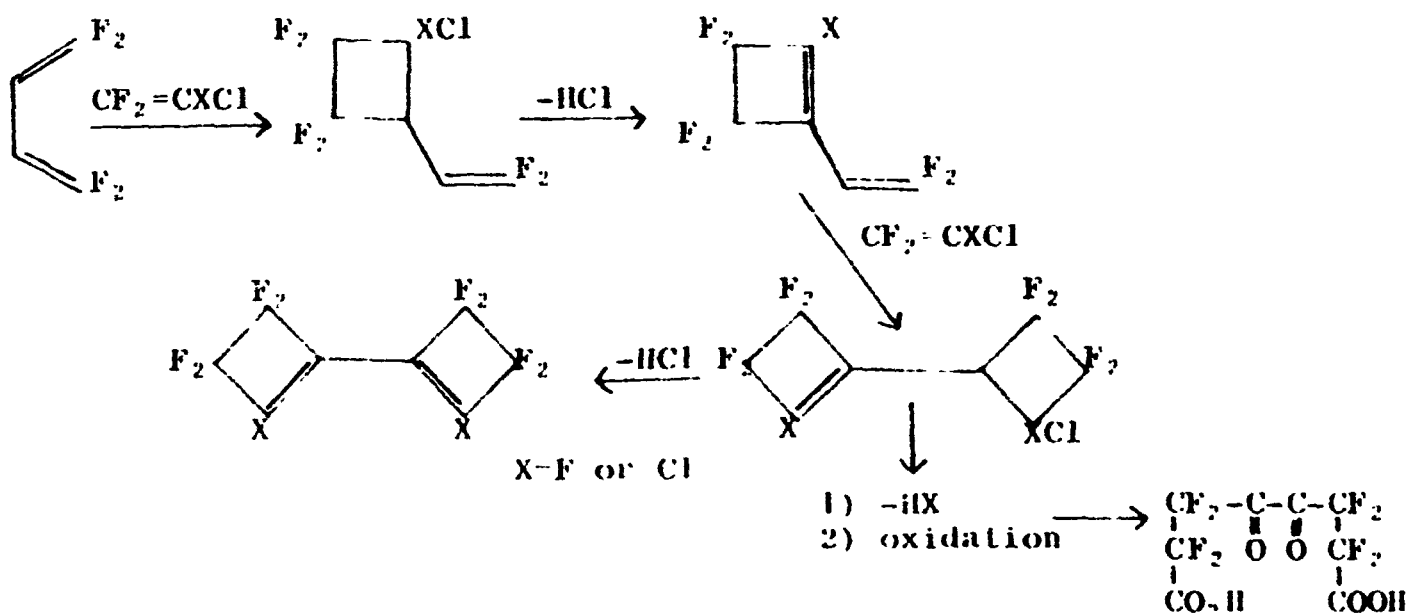
The initial step in developing such a synthesis involves preparation of the butadiene. Two syntheses of 1,1,4,4-tetra-fluorobutadiene have been reported to give rea-onable yields from available starting materials.

Anderson, Putnam, and Sharkey[8] report the thermal scission of 3,3,4,4-tetrafluorocyclobutene at 550-750° and 5-25 mm to give the desired butadiene quantitatively. In the same paper they report preparation of the butadiene by copyrolizing equimolar amounts of acetylene and tetrafluoroethylene at 600° and 1 atm. This reaction is postulated to proceed via the cyclobutene.
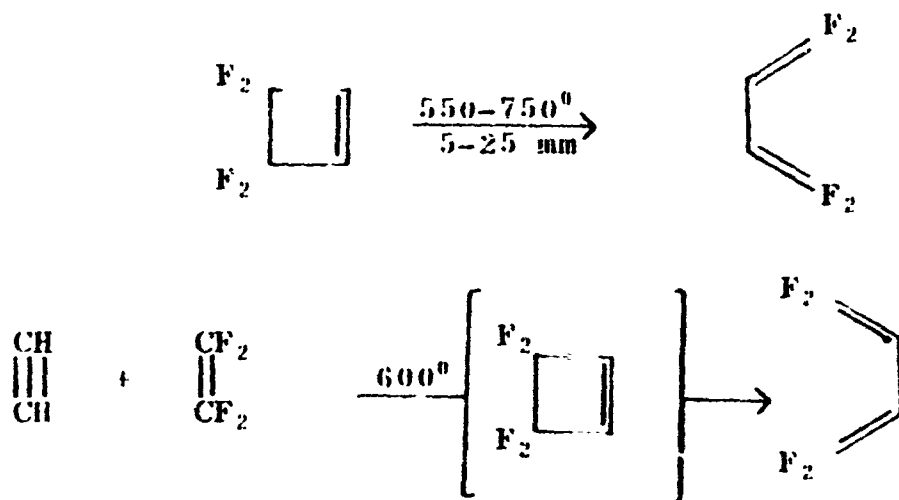
Two further syntheses of the diene logically develop from the work of Haszeldine and Osborne.[9] They are outlined below:

II
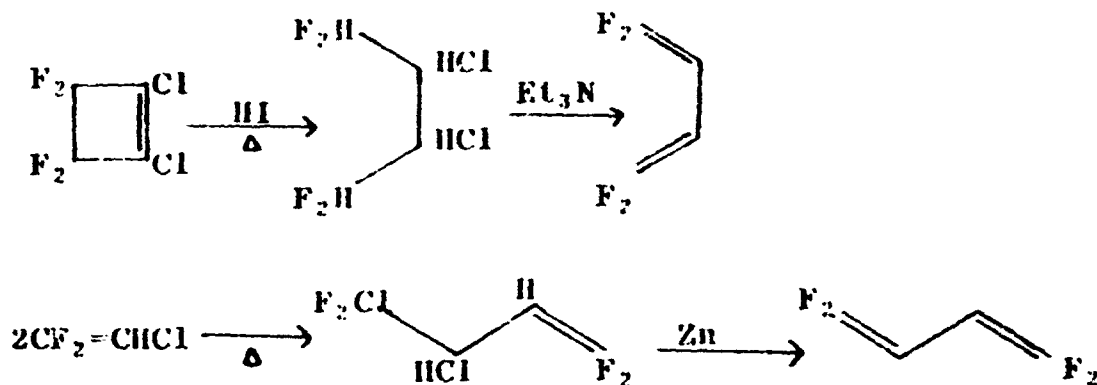
To date the following route has been successfully used to prepare the desired diene:
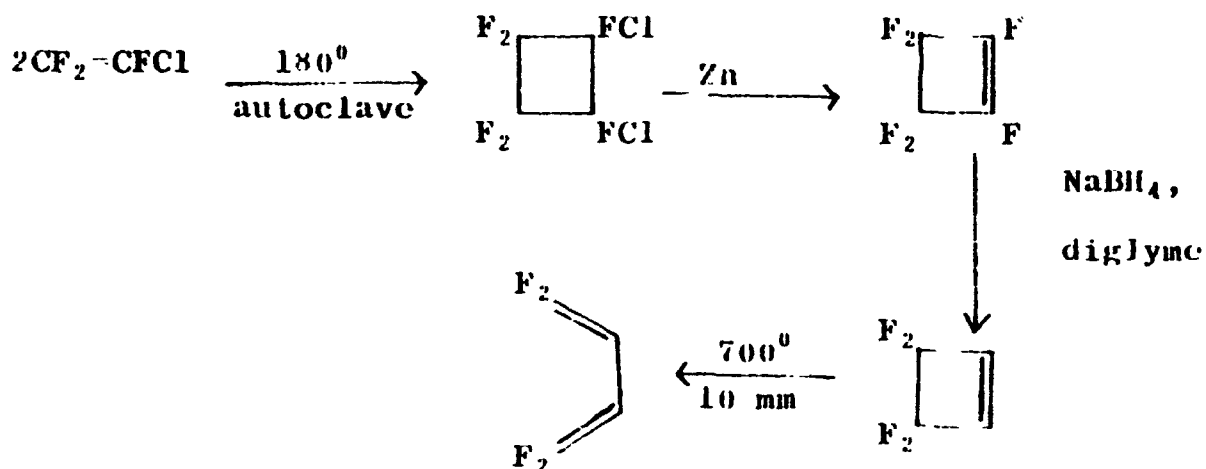


The first two steps of this sequence proceed in excellent yield to afford perfluorocyclobutene. Reduction of this cyclobutene with sodium borohydride in diglyme, however, has been accomplished only in ~ 35 percent yield. Burton[10] reports this reaction to proceed in 55 percent yield. No reason for this discrepancy is apparent. Pyrolysis of 1,2-dihydrotetrafluorocyclobutene proceeds quantitatively.

Reaction of the diene in a heated autoclave with four mole-equivalents of chlorotrifluoroethylene gave 1-(β,β-difluoro)-vinyl-2,3,3,4,4-pentafluoro-2-chlorocyclobutane (I) in 70% yield along with the expected 1,2-dichlorohexafluorocyclobutane and a small higher boiling fraction. The high boiling residue was separated by GLC in hope of obtaining some diadduct. The major fraction (75%) of the residue, however, was identified as 1,2-(β,β-difluoro)-divinyl-hexafluorocyclobutane ($\square$) by comparison with the properties reported for this compound by Putnam, Anderson and Sharkey[11], reported $N_D^{25}$, 1.3458; found, 1.3456 at $25^0$. IR-reported and found peaks at: 3080 (vin-H), 2950 (allyl H), 1755 ($CF_2=CH$), 1405, 1350, 1305, 1255, 1165, 1080, 922, 906, 814. 759.

Failure of any diadduct to result from this reaction is surprising in view of Frank's work cited earlier. I is surely more activated to cycloalkylation than the analogous vinyl compound due to the $CF_2$ moiety. It remains possible, though, that the temperature of the reaction was not sufficient to initiate the second addition.

The next step in the synthesis is dehydrohalogenation of I to regenerate the diene system and thus activate the molecule to cycloalkylation. These reactions are currently in progress.

EXPERIMENTAL:

Synthesis of 1-(β,β-difluoro)-vinyl-2,3,3,4,4-pentafluoro-2-chlorocyclobutane (I).

A 500 ml. stainless steel autoclave was charged with 46.2 gm. of 1,1,4,4-tetrafluorobutadiene, 215 gm. of chlorotrifluoroethylene, and 5 ml. of d-limonene. The mixture was allowed to slowly warm to room temperature and then to $90^0$ after twelve hours. The temperature was increased to $135^0$ at twenty-four hours and $160^0$ at thirty-six hours. This was maintained for twelve hours. The autoclave was vented at room temperature but only traces of gas were evolved. The pale yellow liquid product was fractionally distilled to give 53.7 gm. of a clear colorless liquid, b.p. $75-78^0$ at 629 mm. IR: peaks at 3120, 2990, 1750 plus numerous peaks in the region 750 to 1400 $cm^{-1}$.

Anal. Calcd. for $C_6H_2ClF_7$: C, 29.7; H, 0.83; Cl, 14.6; F, 54.9.

Found : C, 27.51; H, 1.12; Cl, 13.53; F, 57.77.

Plans for Future: It is planned to work further with the unsaturated "dibox" derivatives in the hopes of synthesizing dinitroso compounds from the diketo dibasic acids.

## REFERENCES:

1. W. C. Frank, Ph.D. Thesis, University of Colorado (1965).

2. D. D. Coffman, P. L. Barrick, R. D. Cramer, and M. S. Raasch, J. Am. Chem. Soc., 71, 490 (1949).

3. W. I. Miller, U. S. Patent 2,716,141 (1951) to Du Pont (C. A. 50: P7852a).

4. R. L. Pruett, C. I. Bahner, and H. A. Smith, J. Am. Chem. Soc., 74, 1638 (1952).

5. C. M. Sharts and J. D. Roberts, Ibid., 83, 871 (1961).

6. R. M. Ryananova, I. M. Dolgopol'skii, and A. L. Klebanskii, Zhurnal Obshchei Khimii, 6, 356 (1961) (C. A. 55: 27008 f).

7. J. D. Roberts and C. M. Sharts in "Organic Reactions," Vol. 12, John Wiley and Sons, Inc., New York, N. Y., 1962, p.1.

8. J. L. Anderson, R. E. Putnam, and W. H. Sharkey, J. Am. Chem. Soc., 83, 382 (1961).

9. R. N. Haszeldine and J. E. Osborne, J. Chem. Soc., 3880 (1955).

10. D. J. Burton, private communication.

11. R. E. Putnam, J. L. Anderson, and W. H. Sharkey, J. Am. Chem. Soc., 83, 386 (1961).

TITLE:   Further Studies on the Preparation and Reactions of
1,2-diiodo-3,3,4,4-tetrafluorocyclobutene (I). (See
Semi-Annual Report No. 1 for previous work)


Part A.   Synthesis of I.

OBJECT:   To develop the best conditions for reacting potassium
iodide and diglyme with 1,2-dichloro-3,3,4,4-tetrafluorocyclo-
butene (II) to yield I and to effect the complete removal of
solvent I.

RESULTS AND DISCUSSION:   II Was reacted with excess potassium
iodide in diglyme by heating a mixture of the three under reflux
for nine days.  Runs were made with pot temperatures maintained
at 115°C, 135°C, and 155°C.  The latter was the temperature of
slowly refluxing diglyme.  The progress of each reaction was
followed by VPC analysis.  Considerable tar and carbon was formed
in each reaction but the amounts were greatest at higher temper-
atures.  The halogen exchange reaction proceded towards an ap-
parent equilibrium in all cases but with a slightly higher per-
centage of I after nine days at 115°C.  This is probably not
meaningful.  Large differences were observed in the rate of at-
tainment of equilibrium.  At 115°C there was an appreciable dif-
ference between the relative ratios of II, I, and the intermediate
1-chloro-2-iodo-3,3,4,4-tetrafluorocyclobutene (III) between the
fourth and ninth day.  At 155°C the reaction reached equilibrium
by the fourth day with the percent I being twice that of the per-
cent I obtained at 115°C after four days.  The run at 135°C showed
intermediate behavior.  It was thus concluded that a higher reflux
temperature is best since it greatly speeds the halide exchange
reaction without significantly reducing the yield of I.

Complete removal of diglyme from the product, I, has been
a source of considerable difficulty.  Although the ether solvent
is soluble in water, repeated extractions are unable to remove
the last five percent.  For this reason the product mixture from
the reaction was added to twice its volume of water and the re-
sultant mixture steam distilled.  The organic layer was found to
still contain around ten percent ether.  This product, however,
when steam distilled again with a twenty-fold volume of water af-
forded a nearly ether-free organic layer.  A slight modification
of this procedure in which the organic layer was washed by de-
cantation several times with water before the first steam distil-
lation ultimately led to material which contained no ether.

Distillation of the organic residue gave rise to compounds
I, II, and III.  I Still contained a conteminant of unknown origin

in small amounts. On cooling to $-20^0$C a fractional crystalli-
zation was effected. Upon repeating this twice a "PC pure
sample of I could be obtained. The impure fraction from the
fractional crystallization contained nearly thirty percent of
the total I and was thus reserved for further investigation.

## Part B: UV Catalized Reactions of I

**OBJECT:** To study the photochemical reactions of I with part-
icular interest addressed to obtaining coupling products.

**HISTORICAL:** It is well known that the normal carbon-iodine bond
is cleaved by UV irradiation to yield the respective carbon and
iodine radicals. In normal alkyl iodides wavelengths on the
order of $3130A^0$ or shorter are required to effect this clevage.
The products of such reactions can be predicted by examination
of the probable fates of the radicals formed.

Haszeldine[1] has studied the UV absorption spectra of a
number of halogen-containing alphatic iodo compounds and has
correlated the broad absorption maximum in the $2500-3500A^0$
region to structure. In particular, the presence of halogens
in the β-position and the tertiary nature of the carbon to which
iodine is attached will be expected to cause a distinct batho-
chromic shift and an increase in the extinction coefficient of
the absorption. Conversely, the vinyl nature of the carbon-
iodine bond will result in a dramatic shift to shorter wavelength.
This is illustrated in studies by Park, Seffl, and Lacher[2] on
$CF_2 = CFI$ vapor. They observed $\lambda_{max}$ to occur at $2580A^0$. This
is nearly identical to ethyl iodide vapor having $\lambda_{max}$ at $2580A^0$
with an extinction coefficient of 310.

**RESULTS AND DISCUSSION:** Interest in photochemical reactions of
I originated when it was observed that a freshly distilled sample
discolored markedly on standing in a clear bottle exposed to
sunlight. Samples turn pink within a few minutes and then rapidly
progress to deep maroon or brown. A sample in a corked pyrex
flask, however, showed no new peaks by GLC analysis after several
days despite this discoloration. After one month, numerous clear
colorless rhombic crystals separated from the liquid. There was
insufficient sample for characterization beyond a melting point
and infra-red spectrum on the crude solid.

An ultraviolet spectrum of I was obtained in an effort to
seek optimum conditions for photochemical reaction. The com-
pound exhibits a broad absorption band with $\lambda_{max}$ at $2400A^0$ and
$\varepsilon = 2050$. The upper limit of the band occurs at $2970A^0$ where
zero absorbence is found.

The observed spectra is in good general agreement with that predicted for I. The somewhat large extinction coefficient explains the observed high light sensitivity. The sensitivity in Pyrex glassware, however, is not explained since Pyrex affords near zero transmittance below 3650A⁰. It is hoped that this matter will soon be resolved.

Irradiation of I over mercury with a high intensity ultraviolet source gave interesting and unexpected results. Several products were evident by GLC analysis but only one, a solid, was isolated. This solid was purified and identified as 2,2'-diiodo-3,3,4,4,3',3',4',4'-octafluorobicyclobutene (IV).
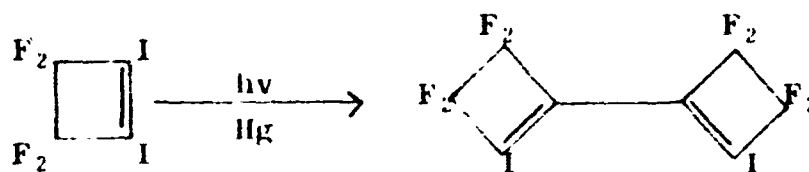


Compound IV will be used to obtain the corresponding dinitroso-derivative.
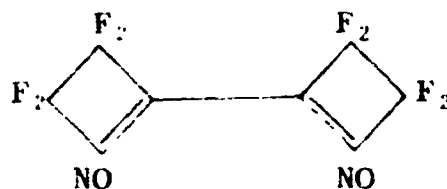


IV, however, does not agree either as to chemical or physical properties with the solid obtained earlier by irradiation in a pyrex vessel. This reaction over mercury now being repeated in an effort to isolate more IV and to characterize the other products. The rate of the reaction with the different ultraviolet sources will also be studied in a crude effort to correlate reactivity to wavelength.

EXPERIMENTAL:

### Sunlight Irradiation of I.

In a 25 ml. Pyrex erlinmeyer flask fitted with a cork was placed 0.2 ml. of I having 4% diglyme as an impurity. The

sample became pink within a few minutes. After 33 days the
sample was deep pink and a few small crystals were evident in
the liquid. The cork was badly stained with iodine. After 85
days the sample was largely converted to several clear colorless
brittle rhombic crystals, m.p. 78-87°. A poor IR in mineral
oil on the crude crystals gave bands at 3500, 1700, 1150, and
770 cm$^{-1}$. There was insufficient sample for analysis or further
characterization.

**Preparation of 2,2'-diiodo-3,3,3',3',4,4,4',4'-octafluoro-
bicyclobutene (IV).** In a quartz U tube fitted with a condenser
was placed 2.0 ml. of Hg and 3.0 ml. of I containing 3% diglyme
impurity. The reaction vessel was suspended inside a Rayonet
Photochemical Chamber Reactor equipped with four RPR-3500A°"black
light" lamps and five RPR-2537A° clear lamps, at an average dis-
tance of two and one-half inches. Within the first few hours the
liquid turned deep brown and I$_2$ crystals formed above the liquid.
During succeeding days the liquid level dropped slightly and
bright mercuric iodide crystals developed. After 24 days numerous
tan crystals were filtered from the mixture. They were recrystal-
lized from CCl$_4$, and ethanol-water. Finally they were sublimed
at 135-145° in a vacuum to yield 61 mg. of white grainy crystals,
m.p. 143-145°. The crystals turn pale yellow on standing. An
IR (mineral oil) was obtained showing peaks at 1530, 1300, 1240,
1120, 820, and 760 cm$^{-1}$.

Anal. Calcd. for C$_8$F$_8$I$_2$:  C, 19.1; F, 30.3; I, 50.5; H, 0.0.
        Found:   C, 18.85; F, 30.91; I, 50.02; H, 0.0.

Part C:  Nitroso Derivatives of I

OBJECT: To prepare 1,2-dinitroso-3,3,4,4-tetrafluorocyclobutene (V).

HISTORICAL: Perfluoroalkylnitroso compounds have been synthesized
in several laboratories in recent years. They have been shown to
form dimers and polymers with perhalo olefins[3,4,5]. The polymers
thus formed can be oils, waxes, or elastimers depending on the
reactants used and the conditions of polymerization. The syn-
thesis of V would make available an important and versatile new
starting material for the development of such polymers.

Previous syntheses of perfluoroalkylnitroso compounds can be
roughly divided into two categories. The first category makes
use of perfluorocarboxylic acid derivatives. Haszeldine[6] was the
first to react the silver salt of trifluoroacetic acid with nit-
rosyl chloride to obtain trifluoronitrosomethane in low yield.
Rosser[7] extended this reaction to get good yields of perfluoro-
nitrosoalkanes and isolated the intermediate perfluoroacyl nitrites.
His work also shed some light on the nature of the Hunsdiecker re-
action occurring during decarboxylation of the intermediate.

This decarboxylation can occur with explosive violence if $R_f$ contains less than three carbon atoms.

$$R_f\overset{O}{\overset{\|}{C}} - OAg \xrightarrow{\text{NOCl}} R_f\overset{O}{\overset{\|}{C}} - ONO \xrightarrow{\Delta} R_f NO + CO_2$$

The second general method of preparation of these nitroso derivatives employs the corresponding perfluoroalkyliodo compounds. Iodine in these compounds is replaced by NO in a photochemically induced free radical reaction in the presence of mercury to remove nitrogen dioxide and iodine[3,4]. This method has been proven useful with compounds containing vinylic iodine[3] and thus seems most adaptable to the proposed synthesis.

$$R_f I \xrightarrow[\text{hv, Hg}]{\text{NO}} R_f NO$$

Detailed experimental plans for the synthesis have not yet been worked out.

**REFERENCES:**

1. R. N. Haszeldine, J. Chem. Soc., 1764, (1953).

2. J. S. Park, R. J. Seffl, and J. R. Lacher, J. Am. Chem. Soc., 78, 59, (1956).

3. C. E. Griffin and R. N. Haszeldine, J. Chem. Soc., 1398, (1960).

4. D. A. Barr and R. N. Haszeldine, J. Chem. Soc., 1881, (1955).

5. D. A. Barr, R. N. Haszeldine, and C. J. Willis, J. Chem. Soc., 1351, (1961).

6. J. Jander and R. N. Haszeldine, J. Chem. Soc., 4172, (1953).

7. R. W. Rosser, Ph.D. Thesis, University of Colorado, (1961).

## PREPARATION OF THE CYCLOPENTENES

Two general synthetic methods were employed in the preparation of the halogenated cycloolefins.

The first involved a catalytic replacement of vinylic chlorine by bromine in the preparation of 1-bromo-2-chlorohexafluorocyclopentene-1 (I) and 1,2-dibromohexafluorocyclopentene-1 (II) from the readily available 1,2-dichlorohexafluorocyclopentene-1 (III). This highly unusual reaction has little precedent in literature.
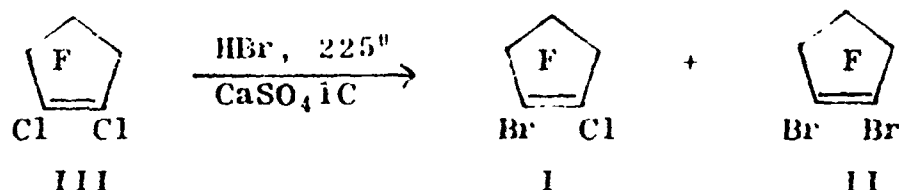


Sharrah[1] reported the addition of hydrogen bromide to chlorotrifluoroethylene ("Freon-1113") yielded 1-chloro-2-bromo-1,2,2-trifluoroethane. Subsequent work in this laboratory has shown that the formation of several more highly brominated products is greatly enhanced by an increase in reaction temperature. The isolation of the more highly brominated products was rationalized by Park and McClure[2] in terms of the formation of vinylic free radicals derived from the initially formed addition product.

The only report of the addition of hydrogen bromide to a halocycloolefin was that of Sharrah[1] who found that hydrogen bromide added to perfluorocyclobutene yielded 1-bromo-2-hydrohexafluorocyclobutane.

When this reaction was extended to 1,2-dichlorotetrafluorobutene (IV)
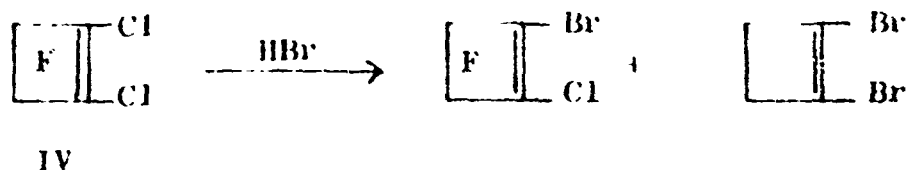


only unreacted starting material and compounds identified as 1-bromo-2-chlorotetrafluorocyclobutene-1 and 1,2-dibromotetrafluorocyclobutene-1 were isolated under the reaction conditions employed.

Similar vinylic substitution was observed with the analogous 1,2-dichlorohexafluorocyclopentene-1 (III). However, the yield was much higher, due presumably to the inherent greater stability of the cyclopentenyl ring to the reaction conditions.

Two mechanistic interpretations are apparent for this reaction.
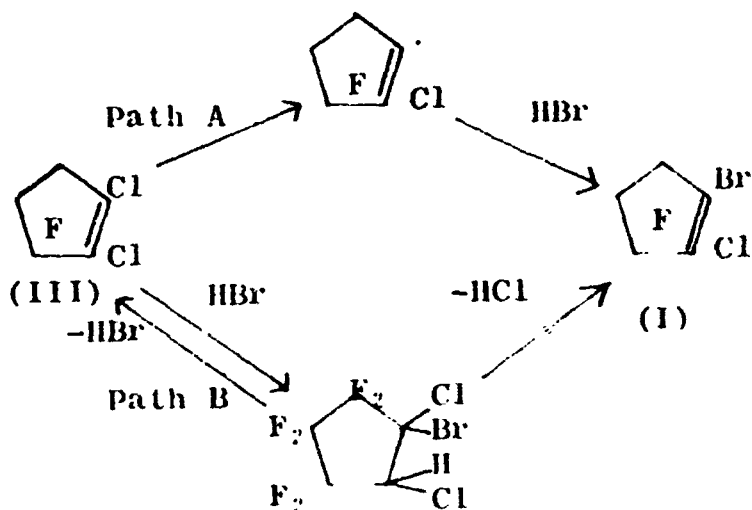


Path A would involve the formation of a vinylic free radical followed by abstraction of bromine from HBr. A second, and more energetically feasible pathway, would require addition of hydrogen bromide to the olefin followed by loss of halogen halide to give either starting material (loss of HBr), or product (loss of HCl). Since an excess of hydrogen bromide was employed, the law of mass action would favor the formation of the product.

Under identical conditions, molecular bromine and (III) did not react.

Baranauckas and Carr[4] have recently reported the isolation of 1,2-dichlorohexafluorocyclopentene from the reaction of 1-chloroheptafluorocyclopentene-1 and hydrogen chloride, a reaction which may be similar in nature.

Halide Ion Attack

The concept of reversible carbanion formation in halocyclobutenes by halide ion attack was developed by Moore[4] in this laboratory. No attempt will be made to cover the fine points inherent to this hypothesis other than to explain the source of some of the synthetic difficulties encountered.

In contrast to the cyclobutenes, acetone was found to be unsuitable as a solvent for halide attack on halocyclopentenes and halocyclohexenes. Either no reaction occurred, or yields of products were low. However, the use of diglyme as a solvent was found to accelerate the conversion to the desired products. It is uncertain, at present, whether the use of diglyme as a solvent favorably alters the equilibrium between reactants and products, or merely serves to kinetically accelerate the reaction because of the higher reaction temperature obtainable with this solvent. Preliminary findings indicate both factors may be involved in the effectiveness of diglyme as a solvent in these reactions.[a]

The chief difficulty inherent to the use of this solvent is in the separation of the halocyclobutene from the diglyme. In several instances, the boiling point of solvent and product are almost identical and combined distillation and aqueous extractions were necessary to isolate a relatively pure product.

Although not actively investigated, the use of similar solvents with somewhat different boiling points, in such cases, would probably be advantageous.

Moore[4] reported the isolation of 1-chloro-2-iodotetrafluorocyclobutene-1 and 1,2-diiodotetrafluorocyclobutene-1 from the reaction of potassium iodide and 1,2-dichlorotetrafluorocyclobutene-1. Unfortunately, the cyclopentenes are not as receptive toward attack by the iodide ion. This was circumvented by employing a starting material with a vinylic halogen more similar in "leaving group ability" to the iodide ion. That is, if $k_{-1} \gg k_2$ for X=Cl, little conversion to the monoiodo-compound would be expected and even less to the diiodo-compound. If the magnitude of $k_{-1}$ and $k_2$ are more nearly equal when X=Br, then increased conversion to the iodo-compounds should be affected. Use of 1,2-dibromohexafluorocyclopentene-1 (II)
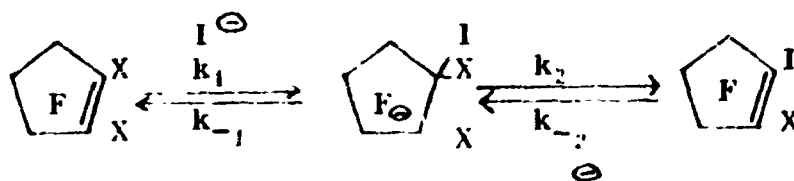


afforded the bromo-, iodo- and diiodo-products in appreciable yields. When large-scale preparative runs were initiated, minor

[a]These findings have recently been verified by Dr. G.G.I. Moore[4], who working independently, has arrived at very similar results.

amounts of unidentified higher boiling compounds were also detected. The identity and source of these compounds is not known at present.

Although the bromochloro- and dibromohexafluorocyclopentenes could also be synthesized through this method using lithium bromide in diglyme, the hydrogen bromide addition-elimination reaction was preferred because of its high yield, freedom from side reactions, and ease or workup.

## EXPERIMENTAL

Analyses were performed by Galbraith Laboratories, Inc., Knoxville, Tennessee. Infrared spectra were taken using a Perkin-Elmer infracord. NMR spectra were obtained using a Varian A-60 analytical spectrometer and pure liquid samples with tetramethylsilane as an internal reference except where otherwise indicated.

**Preparation of 1-bromo-2-chlorohexafluorocyclopentene-1 (I) and 1,2-dibromohexafluorocyclopentene-1 (II).** The reaction was carried out by passing a mixture of the olefin and hydrogen bromide through a 100-cm x 2.5-cm pyrex glass tube packed with a 25/75 $BaSO_4$ activated carbon catalyst heated to ca. $225°C$. The catalyst was prepared in the manner described by Sharrah.[1] In a typical run, 500 gm (2.04 mole) of 1,2-dichlorohexafluorocyclopentene-1 (X) was swept through the tube with about 3.7 molar excess of hydrogen bromide. The crude reaction products were washed with an aqueous sodium bicarbonate solution and twice with 50-ml portions of ice water. The aqueous layers were extracted with two 25-ml portions of diethyl ether and the combined organic layer and ether extracts dried over anhydrous magnesium sulfate. Fractional distillation yielded 275 gm of unreacted X; 128 gm (22% of theory) of 1-bromo-2-chlorohexafluorocyclopentene-1 (I); b.p., $101°C/629$ mm; $d_4^{28}$ 1.92; $n_D^{25}$ 1.3890.

Anal. Calculated for $C_5ClBrF_6$: C, 20.82; Cl, 12.30; Br, 27.71; F, 39.52. Found: C, 20.69; Cl, 12.36; Br, 27.44; F, 39.21. and 106 gm (16% of theory) of 1,2-dibromohexafluorocyclopentene-1 (V); b.p., $119°/629$ mm; $d_4^{28}$ 2.17; $n_D^{25}$ 1.4114.

Anal. Calculated for $C_5Br_2F_6$: C, 17.98; Br, 47.87; F, 34.14. Found: C, 17.95; Br, 47.63; F, 34.02.

The infrared spectra of I and II contained sharp absorption in the olefinic stretching region at 1610 $cm^{-1}$ and 1605 $cm^{-1}$, respectively.

## Preparation of 1-chloro-2-iodohexafluorocyclopentene-1 (V).

1.  A mixture of 70 gm (0.271 mole) of 1.2-dichlorohexafluorocyclo-
pentene-1 (III), 112 gm (0.677 mole) of potassium iodide, and 125 ml
of diglyme was refluxed for 14 days to give a highly discolored
solution containing diglyme, unreacted III, 1-chloro-2-iodohexa-
fluorocyclopentene-1 (V) and traces of several unidentified materials.
Fractional distillation yielded 54.6 gm of 1,2-dichlorohexafluoro-
cyclopentene-1 (III) and 6.8 gm of crude 1-chloro-2-iodohexafluoro-
cyclopentene-1 (V) (7.4% of theory).  Removal of the 5% diglyme
impurity on F. S. 1265 (125) gave pure V, a colorless liquid, b.p.
128°C/ 628 mm; $d_4^{28}$ 2.13; $n_D^{28}$ 1.4268.

Anal.  Calculated for $C_5ClF_6I$:  C, 17.85; Cl, 10.55; F, 33.88;
I, 37.72.  Found:  C, 18.90; Cl, 8.85; F, 33.74; I, 36.27.

The infrared spectrum contained a sharp absorption at 1600 $cm^{-1}$
corresponding to the ( C = C ) stretching frequency.

2.  A mixture of 25 gm (0.102 mole) of 1-bromo-2-chloro-hexa-
fluorocyclopentene-1 (I), 50 gm (0.301 mole) of potassium iodide,
and 75 ml of diglyme were refluxed for 14 days.  Distillation
yielded 14.1 gm of unreacted I and 7.3 gm (22% of theory) of slightly
impure VI.

## Preparation of 1-bromo-2-iodohexafluorocyclopentene-1 (VI) and 1,2-diiodohexafluorocyclopentene-1 (VII).

A mixture of 9.8 gm of
1,2-dibromohexafluorocyclopentene-1 (II), 18.2 gm of anhydrous
potassium iodide, and 50 ml of diglyme were refluxed for 3 days.
Addition of water forced out 11.3 gm of organic product.  Extraction
of the aqueous layer with methylene chloride and distillation of
the combined organic layers gave 3.1 gm unreacted II, 4.6 gm of
1-bromo-2-iodohexafluorocyclopentene-1 (VI) and 3.8 gm of crude 1,2-
diiodohexafluorocyclopentene-1(VIII).

1-Bromo-2-iodohexafluorocyclopentene-1 (VI), b.p. 142°C/628 mm;
$n_D^{28}$ = 1.4488.

Anal.  Calculated for $C_5BrF_6I$:  C, 15.77; Br, 20.98; F, 29.93;
I, 33.32.  Found:  C, 15.86; Br, 21.06; F, 29.85; I, 34.0.

The infrared spectrum of VI contained a sharp absorption at
1590 $cm^{-1}$ corresponding to the ( C = C ) stretching frequency.

1,2-Diiodohexafluorocyclopentene-1 (VIII), b.p. 172°C/631 mm;
$d_4^{20}$ 2.50; $n_D^{28}$ 1.4848.

Anal.  Calculated for $C_5F_6I_2$:  C, 14.03; F, 26.64; I, 59.32.
Found:  C, 15.28; F, 25.16; I, 58.93.

The infrared spectrum of VIII contained a sharp absorption at
1560 $cm^{-1}$ corresponding to the ( C = C ) stretching frequency.

Reaction of 1,2-dichlorohexafluorocyclopentene-1 (III) with Ethanolic Potassium Hydroxide. In a 25-ml, 3-neck, round-bottom flask, fitted with condenser, pressure equalizing addition funnel, and magnetic stir-bar, was placed 10.0 gm (0.0366 mole) of 1,2-dichlorohexafluorocyclopentene-1 (X) in 10 ml of absolute ethanol. After cooling of 0°C. 2.24 gm (0.040 mole) of potassium hydroxide in 10 ml of absolute ethanol were added dropwise with rapid stirring. After addition of the KOH/EtOH solution, the reaction mixture was stirred for an additional 2 hours at room temperature, and then poured into a separatory funnel half-filled with ice water. The reaction flask and filter were washed with methylene chloride which was added to the funnel. The organic layer was drawn off first and washed with water, followed by a wash with saturated sodium chloride solution. The washings and aqueous layer were then extracted with methylene chloride. The organic layer and methylene chloride extracts were combined and dried over anhydrous magnesium sulfate. Fractional distillation yielded 8.1 gm of 1-chloro-2-ethoxyhexafluorocyclopentene-1 (IX). Found: b.p. 137°C/628 mm: $n_D^{28}$ 1.3754. Reported: b.p. 143-144°C/ 750 mm; $n_D^{20}$ 1.3774.

Reaction of 1,2-dibromohexafluorocyclopentene-1 (II) with Ethanolic Potassium Hydroxide. In a 25-ml, 3-neck, round-bottom flask, fitted with condenser, addition funnel, and magnetic stir-bar, was placed 5.0 gm ( 0.0144 mole) of 1,2-dibromohexafluorocyclopentene-1 (XI) in 5 ml of absolute ethanol. After cooling to 0°C, 0.84 gm (0.015 mole) of potassium hydroxide in 3.0 ml of absolute ethanol were added dropwise with constant stirring. The reaction mixture was stirred for an additional 2 hours at room temperature. Distillation yielded 3.8 gm of crude bromo-ether. Pure 1-bromo-2-ethoxyhexafluorocyclopentene-1 (X) was isolated via G.L.C. (10' FS 1265 at 140°C): b.p. 150°C/629 mm; $d_7^8$ 1.72; $n_D^{28}$ 1.3958.

Anal. Calculated for $C_7H_5F_6BrO$: C, 25.11; H, 1.69; Br, 26.73; F, 38.12. Found: C, 25.28; H, 1.82; Br, 26.49; F, 37.79.

The infrared spectrum of X contained a sharp absorption at 1655 cm$^{-1}$ corresponding to the ( C C ) stretching frequency.

The proton NMR of X exhibited a quartet at 5.12 with J 7.0 c.p.s. and a triplet at 8.60 with J 7.0 c.p.s. (integrated areas 2:3) corresponding to the methylene and methyl protons of a vinylic ethoxy group.

Reaction of 1,2-diiodohexafluorocyclopentene-1 (VIII) with Ethanolic Potassium Hydroxide. In a 25-ml, 3-neck, round-bottom flask, fitted with dropping funnel, condenser and magnetic stir-bar, was placed 1.5 gm (0.0034 mole) of 1,2-diiodohexafluorocyclopentene-1 (VIII) in 2 ml of ethanol. After cooling to 0°C, 0.20 gm (0.0036 moles) of potassium hydroxide in 2 ml of absolute ethanol was added dropwise with constant stirring. After addition of the KOH/EtOH solution, the reaction mixture was stirred for an additional

2 hours at room temperature. Workup in the previously described
manner for an alkoxide reaction (see compound IX) yielded 1.1 gm
of crude 1-iodo-2-ethoxyhexafluorocyclopentene-1 (XI). Pure XI
was isolated via preparative scale G.L.C. (18' x 1/4" Ucon 550X
at 150°C); b.p. 172.5°C/628 mm; $d_4^{28}$ 1.78; $n_D^{28}$ - 1.4371.

Anal. Calculated for $C_7H_5F_6IO$: C, 24.30; H, 1.46; F, 32.95;
I, 36.68. Found: C, 25.52; H, 2.36; F, 28.58; I, 36.7.

The infrared spectrum of V contained a ( C   C ) absorption
at 1635 $cm^{-1}$.
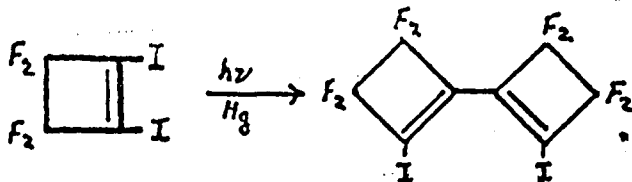
The proton NMR spectrum of XI contained a quartet at 5.43 $\tau$
with J = 7.1 c.p.s. and a triplet at 8.53 $\tau$ with J - 7.1 c.p.s.
corresponding to the methylene and methyl protons of a vinylic
ethoxy group.

ι１

## BIBLIOGRAPHY

1. Park, Sharrah, et al., J. Am. Chem. Soc. 71, 2339 (1949).

2. J. McClure, Ph.D. Thesis, University of Colorado, 1961.

3. Baranaukas and Carr, U. S. Patent, 3,193,587 (July 6, 1965).

4. G. Moore, Ph.D. Thesis, University of Colorado, 1965.

# DOCUMENT CONTROL DATA - R&D

*(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)*

| 1 ORIGINATING ACTIVITY (Corporate author) | 2a. REPORT SECURITY CLASSIFICATION |
|---|---|
| University of Colorado Boulder, Colorado | Unclassified |
| | 2b GROUP |

**3 REPORT TITLE**

THE SYNTHESIS OF SPECIAL FLUORINE-CONTAINING MONOMERS

**4 DESCRIPTIVE NOTES (Type of report and inclusive dates)**

Semi-Annual report #2 - 1 June 1966 - 1 December 1966

**5 AUTHOR(S) (Last name, first name, initial)**

Park, J. D. and Lacher, J. R.

| 6. REPORT DATE | 7a. TOTAL NO. OF PAGES | 7b. NO. OF REFS |
|---|---|---|
| 15 December 1966 | 24 | 4 |

| 8a. CONTRACT OR GRANT NO. | 9a. ORIGINATOR'S REPORT NUMBER(S) |
|---|---|
| DA-19-129-AMC-869(N) | |
| b. PROJECT NO. | Semi-Annual Report No. 2 |
| 1C024401A329 | |
| c. | 9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report) |
| d. | 67-48-CM |

**10. AVAILABILITY/LIMITATION NOTICES**

Distribution of this document is unlimited.
Release to CFSTI and DDC is authorized.

| 11. SUPPLEMENTARY NOTES | 12. SPONSORING MILITARY ACTIVITY |
|---|---|
| | U. S. Army Natick Laboratories Natick, Massachusetts 01760 |

**13. ABSTRACT**

Further work on the syntheses of fluorine containing olefins and diolefins is reported. Studies directed toward syntheses of derivatives of perfluoro-bicyclobutyl and perfluorobicyclobutenyl have been initiated. Of particular interest is the preparation of 2,2'-diiodo-per-fluorobicyclobutenyl by photolysis of 1,2-diiodotetrafluorocyclobutene.



Starting from 1,2-dichlorohexafluorocyclopentene, other dihalo- and mixed dihalohexafluorocyclopentenes have been prepared, and from these have been prepared the monoethoxy derivatives, such as 1-iodo-2-ethoxyhexafluorocyclopentene.

DD FORM 1473
1 JAN 64

| 14. KEY WORDS | LINK A | | LINK B | | LINK C | |
|---|---|---|---|---|---|---|
| | ROLE | WT | ROLE | WT | ROLE | WT |
| Synthesis (Chemistry) | 8 | | | | | |
| Fluorochemicals | 2,4 | | | | | |
| Monomers | 2 | | | | | |
| Fluorine | 2 | | | | | |
| Polymerization | 4 | | | | | |
| Elastomers | 4 | | | | | |

## INSTRUCTIONS

1. ORIGINATING ACTIVITY: Enter the name and address of the contractor, subcontractor, grantee, Department of Defense activity or other organization (corporate author) issuing the report.

2a. REPORT SECURITY CLASSIFICATION: Enter the overall security classification of the report. Indicate whether "Restricted Data" is included. Marking is to be in accordance with appropriate security regulations.

2b. GROUP: Automatic downgrading is specified in DoD Directive 5200.10 and Armed Forces Industrial Manual. Enter the group number. Also, when applicable, show that optional markings have been used for Group 3 and Group 4 as authorized.

3. REPORT TITLE: Enter the complete report title in all capital letters. Titles in all cases should be unclassified. If a meaningful title cannot be selected without classification, show title classification in all capitals in parenthesis immediately following the title.

4. DESCRIPTIVE NOTES: If appropriate, enter the type of report, e.g., interim, progress, summary, annual, or final. Give the inclusive dates when a specific reporting period is covered.

5. AUTHOR(S): Enter the name(s) of author(s) as shown on or in the report. Enter last name, first name, middle initial. If military, show rank and branch of service. The name of the principal author is an absolute minimum requirement.

6. REPORT DATE: Enter the date of the report as day, month, year; or month, year. If more than one date appears on the report, use date of publication.

7a. TOTAL NUMBER OF PAGES: The total page count should follow normal pagination procedures, i.e., enter the number of pages containing information.

7b. NUMBER OF REFERENCES: Enter the total number of references cited in the report.

8a. CONTRACT OR GRANT NUMBER: If appropriate, enter the applicable number of the contract or grant under which the report was written.

8b, 8c, & 8d. PROJECT NUMBER: Enter the appropriate military department identification, such as project number, subproject number, system numbers, task number, etc.

9a. ORIGINATOR'S REPORT NUMBER(S): Enter the official report number by which the document will be identified and controlled by the originating activity. This number must be unique to this report.

9b. OTHER REPORT NUMBER(S): If the report has been assigned any other report numbers (either by the originator or by the sponsor), also enter this number(s).

10. AVAILABILITY/LIMITATION NOTICES: Enter any limitations on further dissemination of the report, other than those imposed by security classification, using standard statements such as:

(1) "Qualified requesters may obtain copies of this report from DDC."

(2) "Foreign announcement and dissemination of this report by DDC is not authorized."

(3) "U. S. Government agencies may obtain copies of this report directly from DDC. Other qualified DDC users shall request through

_____."

(4) "U. S. military agencies may obtain copies of this report directly from DDC. Other qualified users shall request through

_____."

(5) "All distribution of this report is controlled. Qualified DDC users shall request through

_____."

If the report has been furnished to the Office of Technical Services, Department of Commerce, for sale to the public, indicate this fact and enter the price, if known.

11. SUPPLEMENTARY NOTES: Use for additional explanatory notes.

12. SPONSORING MILITARY ACTIVITY: Enter the name of the departmental project office or laboratory sponsoring (paying for) the research and development. Include address.

13. ABSTRACT: Enter an abstract giving a brief and factual summary of the document indicative of the report, even though it may also appear elsewhere in the body of the technical report. If additional space is required, a continuation sheet shall be attached.

It is highly desirable that the abstract of classified reports be unclassified. Each paragraph of the abstract shall end with an indication of the military security classification of the information in the paragraph, represented as (TS), (S), (C), or (U).

There is no limitation on the length of the abstract. However, the suggested length is from 150 to 225 words.

14. KEY WORDS: Key words are technically meaningful terms or short phrases that characterize a report and may be used as index entries for cataloging the report. Key words must be selected so that no security classification is required. Identifiers, such as equipment model designation, trade name, military project code name, geographic location, may be used as key words but will be followed by an indication of technical context. The assignment of links, rules, and weights is optional.